

Novel Approaches to Improve the Microstructure of Alumina Synthesized via the Sol-Gel Method

Yasemin Kenar, Tülin Eruçar, Azade Yelten, İlven Mutlu, Suat Yılmaz

Istanbul University-Cerrahpasa, Department of Metallurgical and Materials Engineering, 34320, Avcılar, Istanbul, Turkey

Sorumlu Yazar / Corresponding Author

Azade Yelten
azade.yelten@iuc.edu.tr

Makale Bilgisi / Article Info

Sunulma / Received : 27/09/2021
Düzeltilme / Revised : 11/11/2021
Kabul / Accepted : 26/12/2021

Destekleyen Kuruluş / Funding Agency

TUBITAK (The Scientific and Technological Research Council of Turkey),
Project #: 106M318
Research Fund of Istanbul University-Cerrahpasa
Projects #: 4201, 37881, FYL-2016-21009, and FYL-2019-29820

Anahtar Kelimeler

Sol-jel
Böhmit
Alümina
Paslanmaz çelik
Mikroyapı

Keywords

Sol-gel
Boehmite
Alumina
Stainless steel
Microstructure

ORCID

Azade Yelten
<https://orcid.org/0000-0001-6089-6257>
Suat Yılmaz
<https://orcid.org/0000-0002-6092-9319>

Abstract

Alumina (Al_2O_3) is a structural ceramic that is used in various high technology applications. Therefore, production of pure Al_2O_3 in different forms draws attention. In this study, porous 17-4 PH stainless steel samples, which were obtained by following the powder metallurgy process based on the space holder-sintering technique were coated with the sol-gel synthesized boehmite ($AlOOH$) gel via dip-coating. The porous steel samples were immersed in the $AlOOH$ gel for 7, 14, and 21 days. Then, the $AlOOH$ coated porous 17-4 PH stainless steel samples were heat treated at $1260^\circ C$ for 40 min. to transform the $AlOOH$ phase into the stable $\alpha-Al_2O_3$ phase. By this way, it was aimed to improve the surface properties of the steel samples, which can be used as implant materials for biomedical applications. In this context, $\alpha-Al_2O_3$ coating formed on the porous steel samples was examined by utilizing from Scanning Electron Microscope (SEM) and Energy Dispersive Spectroscopy (EDS). It is determined that as the immersion time increased, a thicker $\alpha-Al_2O_3$ layer developed on the metal surface. This indicates that $\alpha-Al_2O_3$ coated porous 17-4 PH stainless steel implants may be more resistant to the corrosive body fluids such as saliva.

Sol-Jel Metodu ile Sentezlenmiş Alüminanın Mikroyapısını İyileştirmek için Yeni Yaklaşımlar

Özet

Alümina (Al_2O_3) çeşitli ileri teknoloji uygulamalarında kullanım alanı bulan bir yapısal seramiktir. Dolayısıyla Al_2O_3 'ün farklı formlarda üretilmesi dikkat çeken bir konudur. Bu çalışmada, toz metalurjisi prensibini esas alan boşluk yapıcı sinterleme tekniği doğrultusunda hazırlanan poroz 17-4 PH paslanmaz çelik örnekleri, sol-jel yöntemi ile sentezlenmiş böhmite ($AlOOH$) jeli ile kaplanmıştır. Poroz çelik örnekler $AlOOH$ jeline daldırılmak suretiyle 7, 14 ve 21 gün jel içerisinde bekletilmiştir. Örnekler, daha sonra, jelden çıkartılarak $AlOOH$ fazının kararlı $\alpha-Al_2O_3$ fazına dönüşebilmesi için $1260^\circ C$ 'de 40 dk. sinterlenmiştir. Böylelikle biyomedikal uygulamalarda implant malzemesi olarak da kullanılabilen söz konusu çelik örneklerin yüzey özelliklerinin iyileştirilmesi hedeflenmiştir. Bu bağlamda, çelik örneklerin yüzeyinde oluşan $\alpha-Al_2O_3$ kaplama tabakası Taramalı Elektron Mikroskopu (SEM) ve Enerji Dağılım Spektrometresi (EDS) yardımıyla incelenmiştir. Daldırma süresi arttıkça, metal yüzeyinde daha kalın bir kaplama tabakasının geliştiği belirlenmiştir. Bu durum, $\alpha-Al_2O_3$ ile kaplanmış poroz 17-4 PH paslanmaz çelik implantların saliva (tükürük) gibi korozif vücut sıvılarına karşı daha dirençli olabileceğine işaret etmektedir.

1. INTRODUCTION

Alumina (Al_2O_3) is a popular ceramic material for high technology applications which stands out with its unique thermal, chemical, electrical, optical characteristics, and advanced mechanical properties.¹ Pure and submicron sized fine α - Al_2O_3 powders can be produced, and surface coatings can be prepared practically via the sol-gel method.²⁻⁵ Despite all these superior features, the essential problem of α - Al_2O_3 obtained by the sol-gel method is the needle-like and porous morphology of the synthesized particles. This yields to final products with lower hardness and mechanical strength, which significantly limits the structural properties.²⁻⁷ However, sol-gel derived α - Al_2O_3 can be implemented as also coatings, which are extensively used to enhance the surface characteristics of the materials.

Conventional Al_2O_3 production routes start with the bauxitic ores. These (mechanical methods) can be defined as "top-down", while the chemical production methods, where the sol-gel technique is also included, are expressed as "bottom-up". The hardness of α - Al_2O_3 with full density and naturally high strength produced with the top-down method from the bauxite ores is 2.000 HV.¹ When the morphology of the crystal is examined, it is seen that it has a spherical shape and granular type. It is known that this structure has high density and mechanical strength as a result of grain growth through the solid-state diffusion mechanism during sintering.

Sol-gel technique is a good example of bottom-up (solution-to-solid) production method, which involves processes related to the conversion of the boehmite (AIOOH) gel to the final α - Al_2O_3 phase. Pure, fine, and submicron size α - Al_2O_3 powders can be synthesized through the sol-gel process. Moreover, different morphologies such as fibers, granules, membranes or coatings can be also synthesized via the sol-gel route, as mentioned above.^{1,2,5,6}

There are several studies based on coating the metallic surfaces such as Ti discs⁸, Ti6Al4V substrates⁹, Inconel-718 substrates¹⁰, etc. with sol-gel synthesized α - Al_2O_3 phase in the literature. Nevertheless, there are limited research about coating the surface of highly porous biocompatible metallic materials with sol-gel derived α - Al_2O_3 . In fact, in this study, α - Al_2O_3 coatings were developed on the highly porous 17-4 PH martensitic stainless steel foam samples through the dip-coating principle in the sol-gel synthesized AIOOH gel for 7, 14, and 21 days and then sintering. It was aimed to improve the surface characteristics of the porous steel samples, which can be used as implant materials for biomedical applications. Crystal structure and morphology properties of the prepared samples were characterized with X-Ray Diffraction (XRD) and Scanning Electron Microscope/Energy Dispersive Spectroscopy (SEM/EDS) analyses.

The main purpose of this study is to enhance the surface properties of the porous 17-4 PH stainless steel samples, which can be used as implant materials for biomedical applications by coating the samples with the sol-gel synthesized α - Al_2O_3 phase.

2. METHODS

2.1. Preparation of the Boehmite (AIOOH) Gel and the α - Al_2O_3 Particles

Similar experimental procedure, which was reported in our previous studies^{5,6,11,12} was also applied in the current work. Initially, AIOOH sol was synthesized via the sol-gel process by using aluminum isopropoxide (AIP, $\text{Al}(\text{OC}_3\text{H}_7)_3$, Aldrich, $\geq 98\%$) as the starting material (Fig. 1). Distilled water/AIP molar ratio was determined as 100 depending on the Yoldas principle.^{2,6} 40 moles of distilled water was heated up to 90 °C in a glass reactor with a heater equipped magnetic stirrer. The temperature was adjusted to ~90 °C. 0.4 moles of AIP was added to the distilled water when the temperature was reached to 90 °C, so that the hydrolysis reactions started. After stirring for 1h, HCl (Merck, 37%) diluted up to 10% was added to the solution for the peptization step. At the end of the preparation process, pH of the AIOOH sol was measured as ~2.5. AIOOH sol was gelled at 110 °C in an oven and then heat treated at 1300 °C and 1450 °C in order to achieve the α - Al_2O_3 phase (Fig. 2).

2.2. Production of the Porous 17-4 PH Stainless Steel Samples

Porous 17-4 PH stainless steel specimens for biomedical implant applications were produced by the powder metallurgy-based space holder-sintering technique. Gas atomized spherical shaped 17-4 PH stainless steel powders were employed to fabricate the foams. Composition of the 17-4 PH stainless steel powder was about 4.5% Ni, 15.3% Cr, 0.8% Mo, 0.5% Nb, 4.8% Cu, 1.3% Si, 0.08% C and balance Fe. Average particle size of the steel powders was ~14 μm . Carbamide was used as the space holder (pore former) for its ease of dissolution in water. Amorphous boron powder (Merck, Germany) was added to the 17-4 PH stainless steel powders to create liquid phase sintering and the average particle size of the boron powder was ~2 μm .¹³⁻¹⁵ 17-4 PH stainless steel powders were mixed with 0.5 wt.% boron powder. Polyvinyl alcohol (PVA) was used as a polymer based binder to provide green strength. Carbamide was moistened with water to form a sticky surface and then the steel powder was added. The covered carbamide particles were compacted at 180-200 MPa into cylindrical specimens with a diameter of 12 mm and height of 18 mm. Green specimens were immersed in water at room temperature to leach the carbamide out. PVA in the green specimens was thermally removed in the sintering cycle. Sintering was carried out at 1260 °C for 40 min. in hydrogen atmosphere in a horizontal tube furnace.

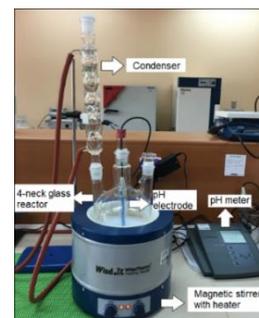


Figure 1. The experimental setup used for synthesizing the AIOOH sol via the sol-gel process.

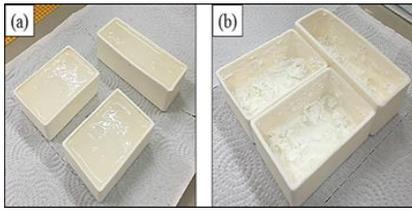


Figure 2. (a) AIOOH gels placed in alumina crucibles before heat treatment and (b) α -Al₂O₃ powders obtained after the heat treatment at 1300°C and 1450°C.

2.3. Dip-coating process

Porous 17-4 PH stainless steel samples were manually placed in the AIOOH gel-filled glass bottles so that all samples were covered with the gel. The lids of the crucibles were tightly closed, hence contact of the samples with air was prevented. The samples were left to be treated in the AIOOH gel for 7, 14, and 21 days (Fig. 3). At the end of the holding time, the coated samples were heat treated at 1260 °C for 40 min.

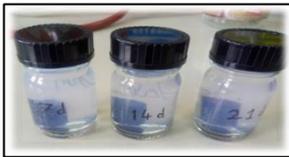


Figure 3. Porous 17-4 PH stainless steel samples immersed in the AIOOH gel.

3. RESULTS AND DISCUSSION

According to the XRD analysis and SEM/EDS results obtained from the stainless-steel samples, which were kept in the AIOOH gel for 7, 14, and 21 days, it was observed that “porous” α -Al₂O₃ particles accumulated on the stainless steel surfaces and a coating layer formed on all of the samples. It was also detected from the XRD analysis that Fe₂O₃, Fe₃O₄ and Fe₄O₅ phases existed between the stainless steel and α -Al₂O₃ layer. It is understood that these intermetallic compounds formed during the conversion procedure from the AIOOH phase to the stable α -Al₂O₃ phase as the temperature increased. Depending on the EDS analysis, when Al-34wt.% and O-28wt.% is proportioned, a value is achieved, which is very close to the stoichiometric ratio of Al₂O₃. The crystal grain sizes of the α -Al₂O₃ deposited on the interfacial layer were measured as ~0.1-0.3 μ m. The thickness of the α -Al₂O₃ layer deposited on the stainless steel surfaces was determined as ~0.2 mm.

It is experienced from our previous studies [5,6] that the α -Al₂O₃ particles produced by the sol-gel method is needle-like and porous, which can be also realized in Fig. 4 and Fig. 5. However, it was observed that the applied heat treatment temperature could be effective on achieving fine particles. In fact, α -Al₂O₃ particles formed after the heat treatment at 1450 °C show better characteristics in terms of particle shape and uniformity than that of the ones obtained as a result of the heat treatment at 1300 °C (Fig. 6). Conversely, higher heat treatment temperatures may also cause abnormal grain growth phenomena, which led us to carry out the heat treatment at 1300 °C. Therefore, the physical and mechanical properties of the sol-gel derived α -Al₂O₃ could not reach to the highest values that α -Al₂O₃ should have. These outcomes demonstrated that longer curing/immersion durations can positively

contribute to the crystalline grain structure of the sol-gel derived α -Al₂O₃ phase formed on the porous 17-4 PH stainless steel substrates. Microstructure images in Fig. 7 show that as the curing time increased, grain growth developed, and spherical shaped grains formed. It is assumed that curing the porous 17-4 PH stainless steel samples in the AIOOH gel improved the crystal morphology of the α -Al₂O₃ phase. This situation is more distinct for the sample that was immersed in the AIOOH gel for 21 days.

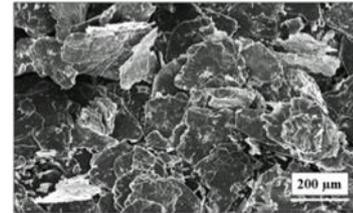


Figure 4. SEM micrograph of the Al₂O₃ coated graphite heat treated at 1300 °C.

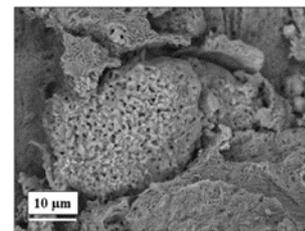


Figure 5. SEM images of the Al₂O₃-BHA (bovine hydroxyapatite) composites heat treated at 1300 °C.

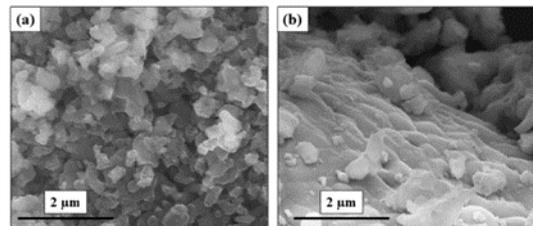


Figure 6. SEM images of the α -Al₂O₃ powders, which were sol-gel synthesized and then heat treated at (a) 1300 °C and (b) 1450 °C.

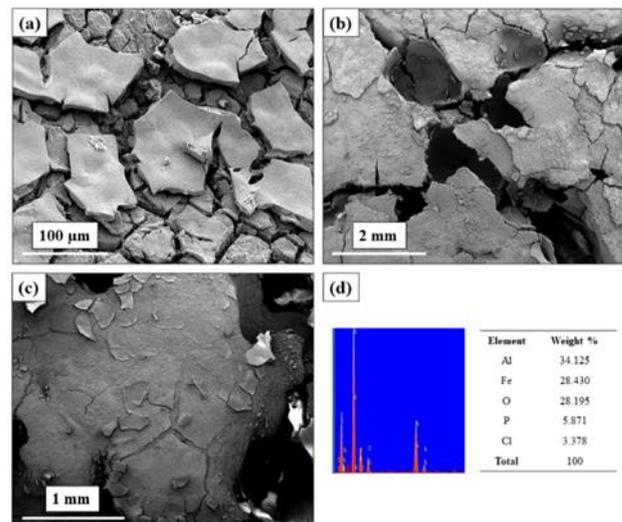


Figure 7. SEM images of the α -Al₂O₃ coated stainless steel surfaces after being immersed in the AIOOH gel for (a) 7, (b) 14, (c) 21 days, and (d) EDS result of the α -Al₂O₃ coated stainless steel surface, which was immersed in the AIOOH gel for 21 days.

4. CONCLUSIONS

Metallic biomaterials possess a great place among the other biomaterials due to their important properties such as machinability, corrosion resistance, being cost-effective, etc. Therefore, various researches continue to enhance the characteristics of the metallic materials to be safely used in biomedical applications for longer service times. In this work, porous 17-4 PH stainless steel samples were produced and then coated with sol-gel synthesized α -Al₂O₃ phase to acquire superior surface features. It is determined that as the curing time in the sol-gel produced AIOOH gel increased from 7 days to 21 days, grain growth developed and spherical shaped grains formed, which indicates the improvement in the crystal morphology of the α -Al₂O₃ phase evolved on the porous steel surfaces.

- Porous 17-4 PH stainless steel substrates were prepared with the powder metallurgy procedure.
- Steel foam samples were then immersed in the sol-gel synthesized AIOOH gel for 7, 14, and 21 days and then sintered to obtain the α -Al₂O₃ phase on the steel surface.
- It was understood that the longer curing/immersion durations can positively contribute to the crystalline grain structure of the sol-gel derived α -Al₂O₃ phase formed on the surface of the porous steel samples.

References

- [1] R.H. Doremus, “Alumina”, *Ceramic and Glass Materials: Structure, Properties and Processing*, J.F. Shackelford, R.H. Doremus (Eds.), Springer, 1-26 (2008).
- [2] B.E. Yoldas, “Technological significance of sol-gel process and process-induced variations in sol-gel materials and coatings”, *Journal of Sol-Gel Science and Technology*, **1**, 65-77 (1993).
- [3] S. Yilmaz, Y. Kutmen-Kalpakli, E. Yilmaz, “Synthesis and characterization of boehmitic alumina coated graphite by sol-gel method”. *Ceramics International*, **35** (5) 2029-2034 (2009).
- [4] E. Yilmaz, S. Yilmaz, “Investigation of properties of boehmitic sol coated graphite added alumina-low cement castables”, *Journal of Ceramic Processing Research*, **11** (1) 56-60 (2010).
- [5] A. Yelten, S. Yilmaz, F.N. Oktar, “Sol-gel derived alumina-hydroxyapatite-tricalcium phosphate porous composite powders”, *Ceramic International*, **38** (4) 2659-2665 (2012).
- [6] A. Yelten, S. Yilmaz, F.N. Oktar, “Comparison of microstructures of bovine hydroxyapatite and sol-gel derived porous alumina-hydroxyapatite biocomposite powders”, *Key Engineering Materials*, **493-494**, 551-555 (2012).
- [7] M. Kumagai, G. Messing, “Controlled transformation and sintering of a boehmite sol-gel by α -alumina seeding”, *Journal of the American Ceramic Society*, **68**, 500-505 (1985).
- [8] M. Dressler, M. Nofz, R.S. Neumann, I. Dorfel, M. Griepentrog, “Sol-gel derived alumina layers on nickel-base superalloy Inconel-718 (IN-718)”, *Thin Solid Films*, **517** (2), 786-792 (2008).
- [9] Z. Evis, R.H. Doremus, “Coatings of hydroxyapatite-nanosize alpha alumina composites on Ti-6Al-4V”, *Materials Letters*, **59** (29-30) 3824-3827 (2005).
- [10] W.Z. Jun, H.L. Ping, C.Z. Zhang, “Fabrication and characterization of hydroxyapatite/Al₂O₃ biocomposite coating on titanium”, *Transactions of Nonferrous Metals Society of China*, **16** (2) 259-266 (2006).
- [11] B. Orbay, A. Yelten, S. Yilmaz, “Microstructural investigation of sol-gel derived seeded alumina powders”. *19th International Metallurgy & Materials Congress*, 534-536 (2018).
- [12] A. Yelten, B. Orbay, S. Yilmaz, “Seeding effect: impact and consequences on the characteristics of sol-gel derived α -Al₂O₃”. *Inorganic and Nano-Metal Chemistry*, available online DOI: 10.1080/24701556.2021.1978495 (2021).
- [13] I. Mutlu, E. Oktay, “Processing and properties of highly porous 17-4 PH stainless steel”, *Powder Metallurgy and Metal Ceramics*, **50** (1) 73-82 (2011).
- [14] I. Mutlu, E. Oktay, “Influence of fluoride content of artificial saliva on metal release from 17-4 PH stainless steel foam for dental implant applications”, *Journal of Materials Science & Technology*, **29** (6) 582-588 (2013).
- [15] I. Mutlu, E. Oktay, “Production and aging of highly porous 17-4 PH stainless steel”. *Journal of Porous Materials*, **19**, 433-440 (2012).